

Silicon Doping of Epitaxial Layers of Gallium Oxide by MOCVD

A.O. Efimov^{1,3,*} , S.N. Rodin² , W.V. Lundin² , A.Yu. Ivanov¹ , A.V. Sakharov^{2,3},
D.I. Panov¹ , V.A. Spiridonov¹ , P.A. Bogdanov¹ , A.F. Tsatsulnikov³ , D.A. Bauman¹ 

¹ Institute of Advanced Data Transfer Systems, ITMO University, Kronverkskiy pr., 49, lit. A, St. Petersburg, 197101, Russia

² Ioffe Institute, Politekhnicheskaya, 26, St. Petersburg, 194021, Russia

³ Submicron Heterostructures for Microelectronics, Research and Engineering Center, Russian Academy of Sciences, Politekhnicheskaya, 26, St. Petersburg, 194021, Russia

Article history

Received May 30, 2025

Received in revised form, July 15, 2025

Accepted July 21, 2025

Available online July 30, 2025

Abstract

The article considers homoepitaxy of beta gallium oxide layers doped with silicon grown by metal organic chemical vapor deposition (MOCVD). Epitaxial growth was carried out on substrates of iron doped gallium oxide. Epitaxial layers at different rates of silicon doping from a diluted monosilane and at different temperatures were obtained. The crystal quality of epitaxial layers was analyzed, as well as mobility of electrons and conductivity were measured. The possibility of controlling the electrical properties (such as electron mobility and conductivity) of homoepitaxial gallium oxide layers doped with silicon during growth by the MOCVD method was demonstrated.

Keywords: Gallium oxide; MOCVD; Homoepitaxy; Silicone doping; Electron mobility; Conductivity

1. INTRODUCTION

The most stable β -phase of gallium oxide has the unique properties, such as a large band gap (4.9 eV [1]) and high values of the breakdown field (up to 8 MV/cm according to calculations [2], 5.3 MV/cm in the device [1]), as well as relatively high electron mobility (up to 196 cm²/(V·s) [3]) and radiation resistance [4].

These facts confirm the significance of using this material in the production of power electronic devices and ultraviolet (UV) sensors. Recently, β -Ga₂O₃ has attracted significant attention for its potential use in various applications, including an UV solar radiation detector, gas sensor, photocatalyst and high-power electronic devices [5–9].

Another advantage of β -Ga₂O₃ is the ability to intentionally introduce *n*-type dopants, using a variety of dopant materials, such as Si [10], Sn [11], Ge [12]. Among these dopants, silicon is regarded as a mostly used one to improve the electrical conductivity of β -Ga₂O₃ layers. In addition, doping of gallium oxide with silicon allows to achieve a specific concentration of electrons, which is

necessary for using the material in the production of electronic devices based on gallium oxide [13].

The manufacture of high-quality semiconductor devices, including power electronics devices, requires epitaxial layers with a minimum number of defects, which will primarily be determined by the choice of the substrate material. It is possible to use different substrate materials for epitaxy of various polytypes of gallium oxide. For example, α -Ga₂O₃ and κ -Ga₂O₃ are often grown on sapphire substrates [14,15] and it has been reported about the successful growth of α -Ga₂O₃ layers on a diamond substrate [16]. However, the most effective way to obtain layers with a low defect rate is to use homoepitaxy, which implies matching the substrate material and the epitaxial layer. Thus, another advantage of gallium oxide can be used: the possibility of producing substrates from bulk crystals grown by relatively cheap methods of pulling from the melt, for example, the Czochralski [17] and Stepanov [18] methods.

The process of growing a layer of β -Ga₂O₃ using epitaxy has been explored through various techniques, includ-

* Corresponding author: A.O. Efimov, e-mail: aoefimov@itmo.ru

ing molecular beam epitaxy (MBE) [19–21], metalorganic chemical vapor deposition (MOCVD) [22–24], halide vapor-phase epitaxy (HVPE) [25–28] and low-pressure chemical vapor deposition (LPCVD) [29–31]. Each method comes with its own unique challenges. For example, when using the MBE method to grow $\beta\text{-Ga}_2\text{O}_3$, it has proven difficult to precisely control the n -type doping level, especially at low dopant concentrations. HVPE and LPCVD epitaxial methods are well suited for producing relatively thick films for vertical power devices, but these methods are not ideal for growing complex heterostructures or for precisely controlling epitaxial layers in the nanometer range. MOCVD is the most widely used method for industrial fabrication of semiconductor devices today. However, there is still a need to improve the quality of $\beta\text{-Ga}_2\text{O}_3$ -based epitaxial heterostructures. A detailed understanding of the mechanisms that affect the characteristics of $\beta\text{-Ga}_2\text{O}_3/\beta\text{-Ga}_2\text{O}_3$ and $\beta\text{-(Al}_x\text{Ga}_{1-x})_2\text{O}_3/\beta\text{-Ga}_2\text{O}_3$ epitaxial layers and structures remains an unsolved problem [32]. Thus, based on the characteristics of the methods, the MOCVD process was chosen in our study.

2. METHODS

Bulk crystals of $\beta\text{-Ga}_2\text{O}_3$ were grown using the Czochralski method in the Nika-3 growth installation (FSUE EZAN, Russia). The melt was prepared in the iridium crucible, which has a height of 26 mm and a diameter of 40 mm. The crucible was placed in a thermal zone made of zirconium dioxide. Induction heating was used for melting. The raw material for the melt was Ga_2O_3 powder with a purity of 99.999%. Iron oxide powder (Fe_2O_3) of 99.99% purity (LLC Lanhit, Russia) was added to the charge for alloying. The addition of iron allows for the production of semi-insulating substrates, which makes it possible to measure the electrical properties of the epitaxial layers. The mass fraction of iron in the charge was 0.011%. The growth was carried out at a temperature of about 1850 °C and a pressure of 1.4 bar in a mixture of gases ($\text{Ar} + \text{O}_2$), the oxygen content in the growth atmosphere was about 5 vol.%. Previously grown gallium oxide crystals were used as seeds. The rate of pulling of the crystal was 0.15 mm/min.

The classical approach in the manufacture of bulk crystal substrates requires cutting, as well as mechanical and chemical polishing followed by cleaning. The nature of the cleavage of $\beta\text{-Ga}_2\text{O}_3$ crystals makes it possible to use a different method of manufacturing substrates, which consists in delaminating the bulk crystal along the cleavage plane (100) [33]. Moreover, using this method of obtaining substrates makes it possible to obtain samples with a sufficiently smooth surface without the need for additional processing. In this way, the substrates were obtained in the form of plane-parallel plates about 10×15 mm in size and 0.5 mm thick.

Epitaxial growth of $\beta\text{-Ga}_2\text{O}_3$ layers doped with silicon was carried out on $\beta\text{-Ga}_2\text{O}_3\text{:Fe}$ substrates using MOCVD method at the Epiquep VP-50 facility, upgraded for the growth of oxides. The installation has a horizontal reactor with induction heating. A diluted monosilane (200 ppm) was used for silicon doping.

The carrier gas (nitrogen) flow was 4.5 slm (liters per minute under standard conditions), the oxygen flow was 1 slm, the trimethylgallium flow was 21 micromol/min, and the initial SiH_4 flow was 6.7 nmol/min. Epitaxial growth of the $\beta\text{-Ga}_2\text{O}_3\text{:Si}$ layer was conducted for 60 minutes. The approximate growth rate was 1100 nm/h, which was estimated using a reflectometry system with a He-Ne laser. Four structures were grown at a fixed temperature of 980 °C with varying concentrations of silicon by changing the initial flow of silane (with a decrease in the flow by 2 and 5 times, and a 2-fold increase in the flow). The other 4 structures were grown with a standard silane flow (6.7 nmol/min), but at different temperatures of 1020 °C, 1050 °C, 1060 °C, and 1100 °C, respectively. A DRON-8 X-ray diffractometer (NPO Burevestnik, Russia) was used to analyze the phase composition of structures and their crystalline quality. Images of chip structures were obtained using a scanning electron microscope (Tescan MIRA-3, Czech Republic). The SE detector was used, the accelerating voltage was 2 kV, with the working distance of 7 mm. Gold plating was not used in this study.

Measurements of electron mobility the conductivity of structures were performed at the BIO-RAD HL5200 Hall effect measurement system by the four-point probe van der Pauw method.

3. RESULTS AND DISCUSSION

The X-ray diffraction 2θ - ω scans obtained from the set of samples with different silane fluxes are shown in Fig 1. These curves confirm the presence of only the β -phase of

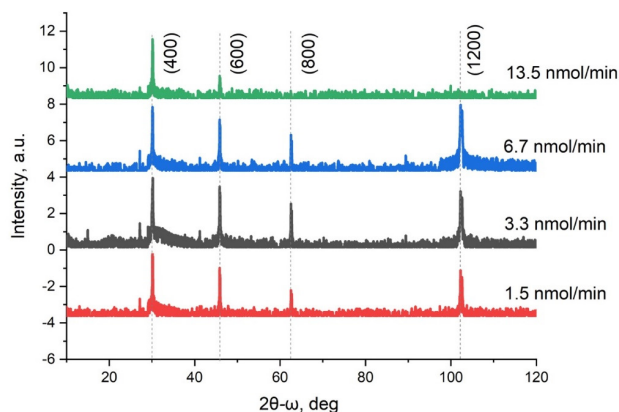


Fig. 1. X-ray diffraction 2θ - ω scans of $\beta\text{-Ga}_2\text{O}_3\text{:Si}$ samples grown at different silane fluxes.

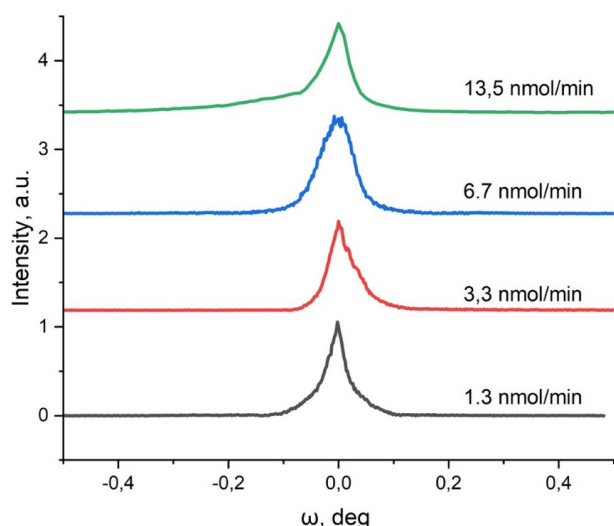


Fig. 2. The rocking curves of the β -Ga₂O₃:Si samples grown at different silane fluxes.

gallium oxide in all epitaxial structures, which is expected for the homoepitaxy process.

Based on the rocking curves for the same structures in Fig. 2, it can be said that the minimal silane flux (1.3 nmol/min) provides the best crystal quality of the structure. On the contrary, an increase in silicon concentration leads to increase in the full width at half maximum (FWHM) from 0.031 to 0.056 of a rocking curve. This is caused by an increase in the number of defects and a deterioration in the crystal quality. For example, authors of Ref. [34] reports that the properties of thin films of gallium oxide grown on (100) substrates are significantly affected by the formation of planar defects, such as packaging defects and twins, which result from the formation of two-dimensional islands with two different orientations rotated 180° in the (100) plane.

An increase in temperature intensified the entry of silicon, which worsened the quality of the layers. The X-ray diffraction rocking curves of the samples grown at different growth temperatures show no significant differences of the quality of these layers. Therefore, their graphs are not given in this work. The similar 2θ - ω curves of the samples grown at different temperatures (see Fig. 3) confirm the presence of only the β -phase of gallium oxide in all structures. Unfortunately, two structures were unsuitable for further measurements (a structure with a silane flux of 3.3 nmol/min and a structure with a growth temperature of 1100 °C). Thus, in the further part of the study, only 6 samples will be considered (obtained under different growth temperatures of 1020 °C, 1050 °C, 1060 °C, respectively and different silane fluxes: 1.3, 6.7, 13.3 nmol/min).

The images of the chip samples were obtained using a scanning electron microscope (Fig. 4) and the thickness of the layers of structures was determined. The thicknesses

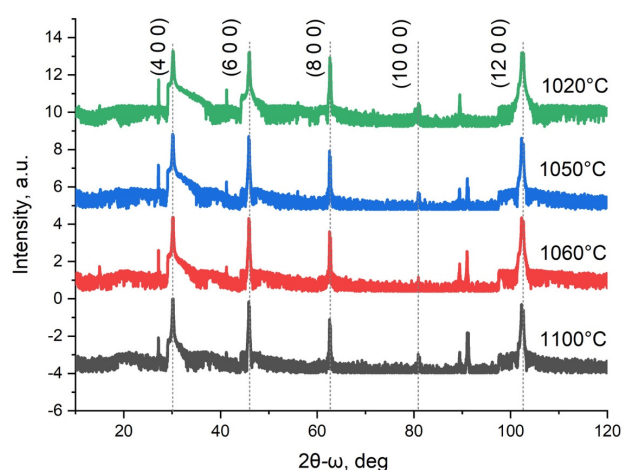


Fig. 3. X-ray diffraction 2θ - ω scans of β -Ga₂O₃:Si samples grown at different growth temperatures.

of the layers were in the range of 0.9–1.0 μ m which are consistent with the results of measurements of the epitaxial growth rate using a reflectometry system. An increase in the growth temperature also had no effect on the growth rate, at least in this temperature range. In addition, based on the images of surface of the sample (see Fig. 5a), it is possible to see the presence of a non-planar growth type. In our experiments, the plane (100) should promote layer-by-layer growth, but due to the lack of misorientation of the substrate (usually by 0.2–0.3° relative to the normal to the growth surface), the density of seed steps on the initial substrate is small and flat areas without steps predominate on the surface of the substrate, which led to island-like layer growth.

Fig. 5 shows the dependence of the electron mobility and the conductivity of three structures with different silane flows. It is easy to see that an increase in the silane flow (and, as a consequence, an increase in the concentration of silicon in the layers) leads to a decrease in the electron mobility. This may be due to scattering by electrons on Si atoms (which are interstitial impurities in gallium oxide) and may also be due to the presence of additional defects in the layer, which is consistent with the data of the X-ray rocking curves.

It is known that dopants and other defects such as interstitials and vacancies may act as scattering centers for electrons which will degrade the mobility. In a recent study [35], it was reported that the mobility of electrons in homoepitaxial films of β -Ga₂O₃ is constrained by the high density of edge dislocations and crystal defects caused by high levels of doping. The nature of the dependencies is comparable with those reported in study [36] in which a decrease in electron mobility with the increase in Si doping concentration suggests the domination of ionized impurity scattering.

The dependence of conductivity (Fig. 6) on the doping level is approximately linear, which is associated with an

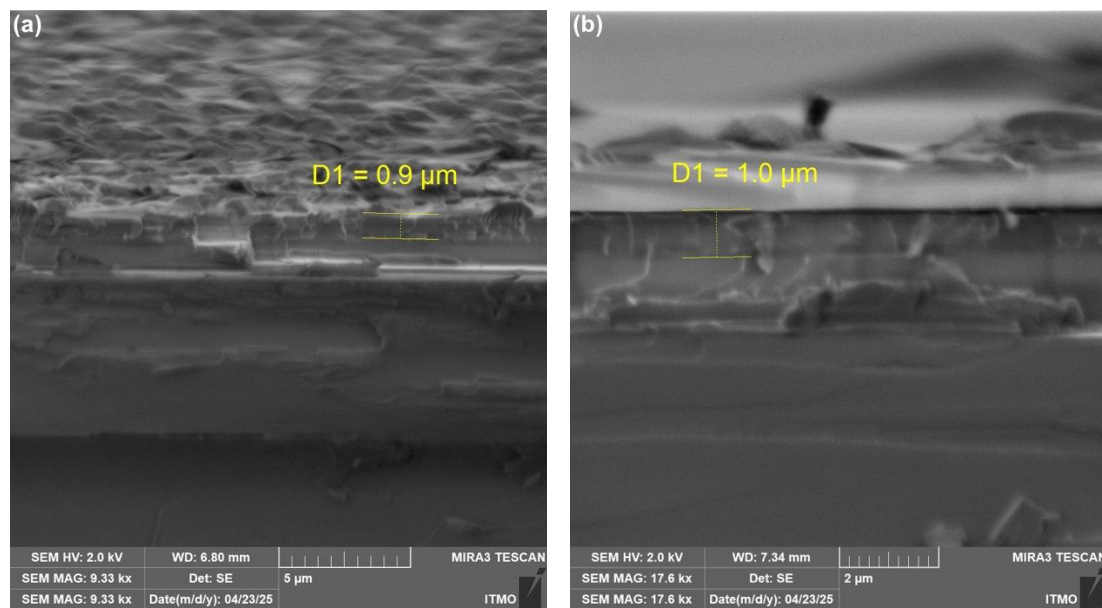


Fig. 4. Images of layers on the chip of structures obtained using a scanning electron microscope: (a) sample with a silane flux of 6.7 nmol/min, a layer of $\beta\text{-Ga}_2\text{O}_3\text{:Si}$ is about 0.9 μm thick; (b) sample with a 3.3 nmol/min silane flux, a $\beta\text{-Ga}_2\text{O}_3\text{:Si}$ layer is about 1.0 μm thick.

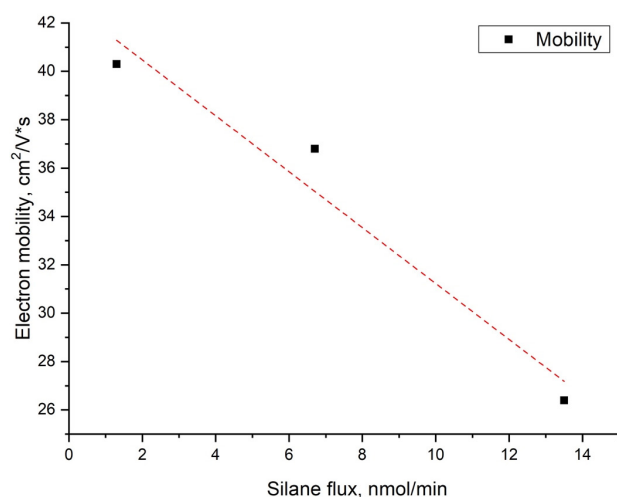


Fig. 5. Dependence of the electron mobility of $\beta\text{-Ga}_2\text{O}_3\text{:Si}$ layers grown at fixed temperature 980 $^\circ\text{C}$ and different silane fluxes on the silane flux.

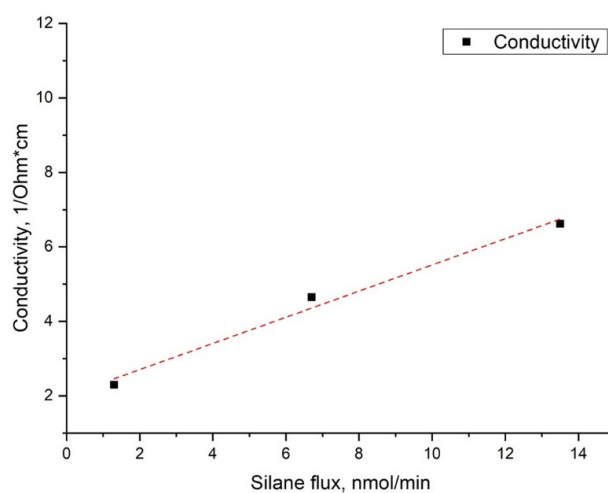


Fig. 6. Dependence of the conductivity of $\beta\text{-Ga}_2\text{O}_3\text{:Si}$ layers grown at fixed temperature 980 $^\circ\text{C}$ and different silane fluxes on the silane flux.

increase in the silicon concentration in the layer, and is consistent with the results of the work [37].

Fig. 7 shows measurements of the conductivity of three structures grown at different growth temperatures. We assume that an increase in temperature leads to the incorporation of larger number of silicon atoms from the silane flux into the epitaxial layer. For example, in work [38] it is reported that a higher growth temperature can contribute to a greater probability of Si entering the epitaxial layer, which further reduces the resistivity of Ga_2O_3 . Due to these factors, the concentration of silicon in the layer and its conductivity increase.

The dependence of electron mobility on the growth temperature of the epitaxial layers is shown in Fig. 8. In the given temperature range, a linear increase in mobility is observed with increasing temperature. We suppose that the main mechanism for limiting electron mobility is its scattering by charged point defects, for example, on vacancies [39]. In this case, as the temperature rises, the silicon content in the layer increases and, as a consequence, the electron concentration increases. In turn, the growth in the electron concentration leads to the screening of charged point defects (scattering centers), to a decrease in scattering and to an increase in mobility.

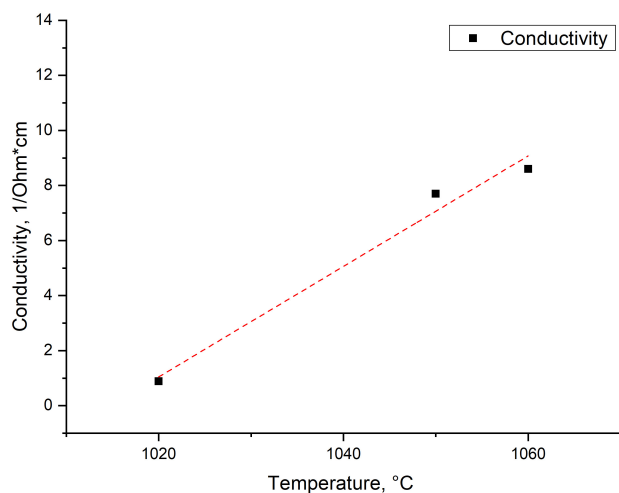


Fig. 7. Dependence of the conductivity of β -Ga₂O₃:Si layers on growth temperature.

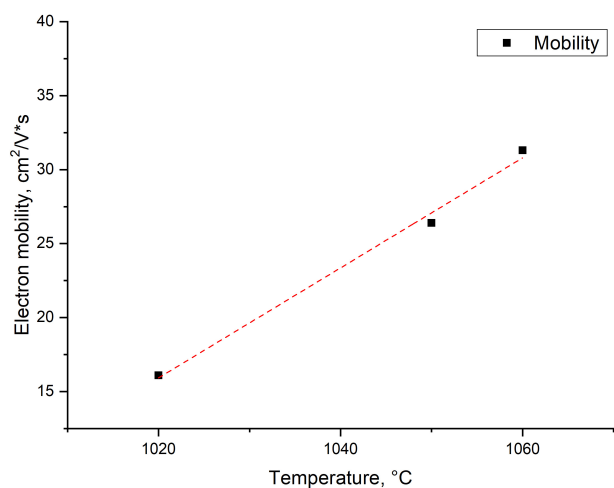


Fig. 8. Dependence of the electron mobility of β -Ga₂O₃:Si layers on different growth temperature.

4. CONCLUSIONS

The paper describes the possibility of homoepitaxial growth of gallium beta oxide layers doped with silicon and a change in their electrical properties depending on the dopant flow and the growth temperature. An increase in the silane flux leads to reduction of the mobility of charge carriers in the layer and deterioration in crystalline quality with an increase of its conductivity. An increase in the growth temperature leads to an increase of the conductivity of structures and the mobility of charge carriers in them with increased crystalline quality.

Thus, the possibility of β -Ga₂O₃ layer growth by MOCVD with control of conductivity and mobility of electrons depending on the growth parameters (temperature and silane flux) has been shown. This result will be crucial for creating efficient power optoelectronic components with a high breakdown field and minimal resistance.

A special feature of this work is the growth of gallium oxide layers on the (100) plane of the substrate, while most papers consider other growth planes, such as (010) [13,23,40] and (001) plane [34]. The effect of doping at high growth temperatures is considered, as opposed to other works, where the epitaxial growth temperature on the (100) plane is fixed and is less than 980 °C, for example, 740 °C [40], 800–900 °C [41], 825 °C [42].

The data obtained in the work will form the basis for future technology for the production of device structures and microelectronic devices based on gallium oxide for promising power electronics devices, such as field-effect transistors and Schottky diodes.

ACKNOWLEDGEMENTS

The authors acknowledge support from the Russian Science Foundation (project No. 24-12-00229). The authors are grateful to Dr. M.V. Dorogov for his help in obtaining images of layers using the SEM.

REFERENCES

- [1] J.A. Spencer, A.L. Mock, A.G. Jacobs, M. Schubert, Y. Zhang, M.J. Tadjer, A review of band structure and material properties of transparent conducting and semiconducting oxides: Ga₂O₃, Al₂O₃, In₂O₃, ZnO, SnO₂, CdO, NiO, CuO, and Sc₂O₃, *Applied Physics Reviews*, 2022, vol. 9, no. 1, art. no. 011315.
- [2] S. Stepanov, V. Nikolaev, V. Bougrov, A. Romanov, Gallium OXIDE: Properties and applica 498 a review, *Reviews on Advanced Materials Science*, 2016, vol. 44, no. 1, pp. 63–86.
- [3] A. Bhattacharyya, C. Peterson, T. Itoh, S. Roy, J. Cooke, S. Rebollo, P. Ranga, B. Sensale-Rodriguez, S. Krishnamoorthy, Enhancing the electron mobility in Si-doped (010) β -Ga₂O₃ films with low-temperature buffer layers, *APL Materials*, 2023, vol. 11, no. 2, art. no. 021110.
- [4] D.A. Bauman, A.I. Borodkin, A.A. Petrenko, D.I. Panov, A.V. Kremleva, V.A. Spiridonov, D.A. Zakgeim, M.V. Silnikov, M.A. Odnoblyudov, A.E. Romanov, V.E. Bougrov, On improving the radiation resistance of gallium oxide for space applications, *Acta Astronautica*, 2021, vol. 180, pp. 125–129.
- [5] B. Zhao, F. Wang, H. Chen, L. Zheng, L. Su, D. Zhao, X. Fang, An ultrahigh responsivity (9.7 mA W⁻¹ self-powered solar-blind photodetector based on individual ZnO–Ga₂O₃ heterostructures, *Advanced Functional Materials*, 2017, vol. 27, no. 17, art. no. 1700264.
- [6] H.J. Lin, H. Gao, P.X. Gao, UV-enhanced CO sensing using Ga₂O₃-based nanorod arrays at elevated temperature, *Applied Physics Letters*, 2017, vol. 110, no. 4, art. no. 043101.
- [7] S. Jin, X. Wang, X. Wang, M. Ju, S. Shen, W. Liang, Y. Zhao, Z. Feng, H.Y. Playford, R.I. Walton, C. Li, Effect of phase junction structure on the photocatalytic performance in overall water splitting: Ga₂O₃ photocatalyst as an example, *The Journal of Physical Chemistry C*, 2015, vol. 119, no. 32, pp. 18221–18228.

- [8] K.Y. Woo, J.H. Lee, K.H. Kim, S.J. Kim, T.G. Kim, Highly transparent conductive Ag/Ga₂O₃ electrode for near-ultraviolet light-emitting diodes, *Physica Status Solidi A*, 2014, vol. 211, no. 8, pp. 1760–1763.
- [9] P. Jaiswal, U. Ul Muazzam, A.S. Pratiyush, N. Mohan, S. Raghavan, R. Muralidharan, S.A. Shivashankar, D.N. Nath, Microwave irradiation-assisted deposition of Ga₂O₃ on III-nitrides for deep-UV opto-electronics, *Applied Physics Letters*, 2018, vol. 112, no. 2, art. no. 021105.
- [10] K.D. Leedy, K.D. Chabak, V. Vasilyev, D.C. Look, J.J. Boeckl, J.L. Brown, S.E. Tetlak, A.J. Green, N.A. Moser, A. Crespo, D.B. Thomson, R.C. Fitch, J.P. McCandless, G.H. Jessen, Highly conductive homoepitaxial Si-doped Ga₂O₃ films on (010) β-Ga₂O₃ by pulsed laser deposition, *Applied Physics Letters*, 2017, vol. 111, no. 1, art. no. 012103.
- [11] Y. Zhang, J. Yan, G. Zhao, W. Xie, First-principles study on electronic structure and optical properties of Sn-doped β-Ga₂O₃, *Physica B: Condensed Matter*, 2010, vol. 405, no. 8, pp. 3899–3903.
- [12] E. Ahmadi, O.S. Koksaldi, S.W. Kaun, Y. Oshima, D.B. Short, U.K. Mishra, J.S. Speck, Ge doping of β-Ga₂O₃ films grown by plasma-assisted molecular beam epitaxy, *Applied Physics Express*, 2017, vol. 10, no. 4, art. no. 041102.
- [13] X. Ji, J. Yue, X. Qi, Z. Yan, S. Li, C. Lu, Z. Li, Z. Liu, S. Qi, X. Yan, J. Wang, S. Wang, P. Li, W. Tang, Homoepitaxial Si-doped Gallium Oxide films by MOCVD with tunable electron concentrations and electrical properties, *Vacuum*, 2023, vol. 210, art. no. 111902.
- [14] A.V. Myasoedov, I.S. Pavlov, A.V. Morozov, A.I. Pechnikov, S.I. Stepanov, V.I. Nikolaev, Dissociation of $\frac{1}{3} < 10\bar{1}1 >$ misfit dislocation at the interface of α-Ga₂O₃ thin film deposited on *m*-plane sapphire, *Materials Science in Semiconductor Processing*, 2024, vol. 184, art. no. 108778.
- [15] O.F. Vyvenko, S.V. Shapenkov, E.V. Ubyivovk, A.S. Bondarenko, A.I. Pechnikov, V.I. Nikolaev, S.I. Stepanov, Twin domain and antiphase boundaries in microcrystals of K-phase Ga₂O₃, *Materialia*, 2023, vol. 32, art. no. 101942.
- [16] A.Y. Polyakov, V.I. Nikolaev, S.A. Tarelkin, A.I. Pechnikov, S.I. Stepanov, A.E. Nikolaev, I.V. Shchemerov, E.B. Yakimov, N.V. Luparev, M.S. Kuznetsov, A.A. Vasilev, A.I. Kochkova, M.I. Voronova, M.P. Scheglov, S.J. Pearton, Electrical properties and deep trap spectra in Ga₂O₃ films grown by halide vapor phase epitaxy on p-type diamond substrates, *Journal of Applied Physics*, 2021, vol. 129, no. 18, art. no. 185701.
- [17] D.A. Zakgeim, D.I. Panov, V.A. Spiridonov, A.V. Kremleva, A.M. Smirnov, D.A. Bauman, A.E. Romanov, M.A. Odnoblyudov, V.E. Bougrov, Volume gallium oxide crystals grown from melt by the Czochralski method in an oxygen-containing atmosphere, *Technical Physics Letters*, 2020, vol. 46, no. 11, pp. 1144–1146.
- [18] D.A. Bauman, D.I. Panov, D.A. Zakgeim, V.A. Spiridonov, A.V. Kremleva, A.V. Asach, E.V. Tambulatova, A.V. Sakharov, A.E. Romanov, High quality β-Ga₂O₃ bulk crystals, grown by edge-defined film-fed growth method: Growth features, structural, and thermal properties, *Journal of Vacuum Science & Technology A*, 2023, vol. 41, no. 5, art. no. 053203.
- [19] T. Oshima, T. Okuno, N. Arai, Y. Kobayashi, S. Fujita, β-Al_{2x}Ga_{2-2x}O₃ thin film growth by molecular beam epitaxy, *Japanese Journal of Applied Physics*, 2009, vol. 48, no. 7R, art. no. 070202.
- [20] K. Sasaki, A. Kuramata, T. Masui, E.G. Villora, K. Shimamura, S. Yamakoshi, Device-quality β-Ga₂O₃ epitaxial films fabricated by ozone molecular beam epitaxy, *Applied Physics Express*, 2012, vol. 5, no. 3, art. no. 035502.
- [21] K. Sasaki, M. Higashiwaki, A. Kuramata, T. Masui, S. Yamakoshi, Growth temperature dependences of structural and electrical properties of Ga₂O₃ epitaxial films grown on β-Ga₂O₃ (010) substrates by molecular beam epitaxy, *Journal of Crystal Growth*, 2014, vol. 392, pp. 30–33.
- [22] G. Wagner, M. Baldini, D. Gogova, M. Schmidbauer, R. Schewski, M. Albrecht, Z. Galazka, D. Klimm, R. Fornari, Homoepitaxial growth of β-Ga₂O₃ layers by metal-organic vapor phase epitaxy, *Physica Status Solidi A*, 2014, vol. 211, no. 1, pp. 27–33.
- [23] M. Baldini, M. Albrecht, A. Fiedler, K. Irmscher, R. Schewski, G. Wagner, Si- and Sn-doped homoepitaxial β-Ga₂O₃ layers grown by MOVPE on (010)-oriented substrates, *ECS Journal of Solid State Science and Technology*, 2016, vol. 6, no. 2, art. no. Q3040.
- [24] Y. Zhang, F. Alema, A. Mauze, O.S. Koksaldi, R. Miller, A. Osinsky, J.S. Speck, MOCVD grown epitaxial β-Ga₂O₃ thin film with an electron mobility of 176 cm²/V s at room temperature, *APL Materials*, 2019, vol. 7, no. 2, art. no. 022506.
- [25] K. Nomura, K. Goto, R. Togashi, H. Murakami, Y. Kumagai, A. Kuramata, S. Yamakoshi, A. Koukitu, Thermodynamic study of β-Ga₂O₃ growth by halide vapor phase epitaxy, *Journal of Crystal Growth*, 2014, vol. 405, pp. 19–22.
- [26] Y. Oshima, E.G. Villora, K. Shimamura, Quasi-heteroepitaxial growth of β-Ga₂O₃ on off-angled sapphire (0001) substrates by halide vapor phase epitaxy, *Journal of Crystal Growth*, 2015, vol. 410, pp. 53–58.
- [27] K. Goto, K. Konishi, H. Murakami, Y. Kumagai, B. Mone-mar, M. Higashiwaki, A. Kuramata, S. Yamakoshi, Halide vapor phase epitaxy of Si doped β-Ga₂O₃ and its electrical properties, *Thin Solid Films*, 2018, vol. 666, pp. 182–184.
- [28] J.H. Leach, K. Udary, J. Rumsey, G. Dodson, H. Splawn, K.R. Evans, Halide vapor phase epitaxial growth of β-Ga₂O₃ and α-Ga₂O₃ films, *APL Materials*, 2019, vol. 7, no. 2, art. no. 022504.
- [29] S. Rafique, L. Han, A.T. Neal, S. Mou, M.J. Tadjer, R.H. French, H. Zhao, Heteroepitaxy of N-type β-Ga₂O₃ thin films on sapphire substrate by low pressure chemical vapor deposition, *Applied Physics Letters*, 2016, vol. 109, no. 13, art. no. 132103.
- [30] S. Rafique, L. Han, M.J. Tadjer, J.A. Freitas, N.A. Mahadik, H. Zhao, Homoepitaxial growth of β-Ga₂O₃ thin films by low pressure chemical vapor deposition, *Applied Physics Letters*, 2016, vol. 108, no. 18, art. no. 182105.
- [31] Z. Feng, M.R. Karim, H. Zhao, Low pressure chemical vapor deposition of β-Ga₂O₃ thin films: Dependence on growth parameters, *APL Materials*, 2019, vol. 7, no. 2, art. no. 022514.
- [32] Y. Lv, J. Ma, W. Mi, C. Luan, Z. Zhu, H. Xiao, Characterization of β-Ga₂O₃ thin films on sapphire (0001) using metal-organic chemical vapor deposition technique, *Vacuum*, 2012, vol. 86, no. 12, pp. 1850–1854.
- [33] D.A. Bauman, D.I. Panov, D.A. Zakgeim, V.A. Spiridonov, A.V. Kremleva, A.A. Petrenko, P.N. Brunkov, N.D. Prasolov, A.V. Nashchekin, A.M. Smirnov, M.A. Odnoblyudov, V.E. Bougrov, A.E. Romanov, High-Quality Bulk β-Ga₂O₃ and β-(Al_xGa_{1-x})₂O₃ Crystals: Growth and Properties, *Physica Status Solidi A*, 2021, vol. 218, no. 20, art. no. 2100335.
- [34] S. Rafique, M.R. Karim, J.M. Johnson, J. Hwang, H. Zhao, LPCVD homoepitaxy of Si doped β-Ga₂O₃ thin films on

- (010) and (001) substrates, *Applied Physics Letters*, 2018, vol. 112, no. 5, art. no. 052104.
- [35] X. Chen, F.F. Ren, J. Ye, S. Gu, Gallium oxide-based solar-blind ultraviolet photodetectors, *Semiconductor Science and Technology*, 2020, vol. 35, no. 2, art. no. 023001.
- [36] R. Miller, F. Alema, A. Osinsky, Epitaxial β -Ga₂O₃ and β -(Al_xGa_{1-x})₂O₃/β-Ga₂O₃ Heterostructures Growth for Power Electronics, *IEEE Transactions on Semiconductor Manufacturing*, 2018, vol. 31, no. 4, pp. 467–474.
- [37] E.G. Villora, K. Shimamura, Y. Yoshikawa, T. Ujiiie, K. Aoki, Electrical conductivity and carrier concentration control in β-Ga₂O₃ by Si doping, *Applied Physics Letters*, 2008, vol. 92, no. 20, art. no. 202120.
- [38] F.G. Tarntair, C.Y. Huang, S. Rana, K.L. Lin, S.H. Hsu, Y.C. Kao, S.J. Pratap, Y. Chen, N. Tumilty, P. Liu, R.H. Horng, Material Properties of n-Type β-Ga₂O₃ epilayers with In Situ Doping Grown on Sapphire by Metalorganic Chemical Vapor Deposition, *Advanced Electronic Materials*, 2025, vol. 11, no. 1, art. no. 2300679.
- [39] X. Zhang, S. Zhang, X. Liang, J.Y. Yang, L. Liu, Effects of temperature and charged vacancies on electronic and optical properties of β-Ga₂O₃ after radiation damage, *Optics Express*, 2023, vol. 31, no. 24, pp. 40765–40780.
- [40] Z. Feng, A.F.M. Anhar Uddin Bhuiyan, M.R. Karim, H. Zhao, MOCVD homoepitaxy of Si-doped (010) β-Ga₂O₃ thin films with superior transport properties, *Applied Physics Letters*, 2019, vol. 114, no. 25, art. no. 250601.
- [41] W. Tang, X. Han, X. Zhang, B. Li, Y. Ma, L. Zhang, T. Chen, X. Zhou, C. Bian, Y. Hu, D. Chen, H. Qi, Z. Zeng, B. Zhang, Homoepitaxial growth of (100) Si-doped β-Ga₂O₃ films via MOCVD, *Journal of Semiconductors*, 2023, vol. 44, no. 6, art. no. 062801.
- [42] A.K. Singh, C.C. Yen, C.Y. Huang, F.G. Tarntair, H.Y. Chou, S.M. Huang, B.K. Yadlapalli, R.H. Horng, D.S. Wu, First-principles investigations and MOCVD growth of Si-doped β-Ga₂O₃ thin films on sapphire substrates for enhancing Schottky barrier diode characteristics, *Materials Science in Semiconductor Processing*, 2024, vol. 178, art. no. 108475.

УДК 538.911

Легирование кремнием эпитаксиальных слоев оксида галлия методом осаждения металлорганических соединений из газовой фазы

А.О. Ефимов^{1,3}, С.Н. Родин², В.В. Лундин², А.Ю. Иванов¹, А.В. Сахаров^{2,3}, Д.Ю. Панов¹, В.А. Спиридонов¹, П.А. Богданов¹, А.Ф. Цацульников³, Д.А. Бауман¹

¹ Институт перспективных систем передачи данных, Университет ИТМО, Кронверкский пр., 49, лит. А, Санкт-Петербург, 197101, Россия

² Физико-технический институт им. А.Ф. Иоффе Российской академии наук, Политехническая ул., д. 26, Санкт-Петербург, 194021, Россия

³ НТЦ микроэлектроники РАН, Политехническая ул., д. 26, Санкт-Петербург, 194021, Россия

Аннотация. В работе рассмотрены особенности легирования кремнием эпитаксиальных слоев оксида галлия в процессе гомоэпитаксии. На легированных железом подложках β-Ga₂O₃ методом осаждения металлорганических соединений из газовой фазы (MOCVD) выращены слои β-Ga₂O₃ легированные кремнием из раствора моносилана при различных потоках силана и температурах роста. Проанализировано кристаллическое качество структур, получены данные подвижности носителей и проводимости слоев в зависимости от параметров легирования.

Ключевые слова: оксид галлия; МОГФЭ; гомоэпитаксия; легирование; подвижность электронов; проводимость